

Construction of a cut-off wall using Mixed-In-Place technology for a flood retention basin in southern Germany

Mostafa Abdelhamid¹, Daniel Junger¹ and Karsten Beckhaus¹

¹ Bauer Spezialtiefbau GmbH, Germany

Abstract. In the area of Feldolling, a village south of Munich, Bavaria, Germany, a flood water retention basin for the river Mangfall is planned and still under construction. In the event of heavy rains or seasonal ice-melting in the Alps, the flood-prone region can suffer from severe damage to the infrastructure and the residential areas. Those events can therefore even threaten people's lives. The planned flood retention basin will store more than 6 Mio m³ of water. For the construction of the retention basin, the authorities are building a few dikes of different lengths in addition to a dam to capture the flood water in the retention basin. The inner sealing and the underground cut-off barrier of one of the dikes was constructed using deep soil mixing wall. The implemented deep soil mixing technique is the Mixed-In-Place technology (MIP).

The MIP wall had a width of 550 mm and reached a maximum depth of 23 m. The soil conditions were not uniform and varied from gravel and sand to silt and clay. The cut-off wall had to have a strength not exceeding 3 MPa and should be 1.5 MPa on average. To take into account the different soil characteristics and to achieve the required material properties, a lab testing program took place before construction.

Keywords: Flood retention basin, Dike, Levee, Cut-off wall, Deep Soil Mixing, Mixed-In-Place, MIP.

1 Introduction

Flood control measures are important nowadays to limit damage for potential infrastructure and private properties, and in worst case scenarios to save people's lives. As a result of the climate change, higher discharges can lead to water overflow from rivers. Especially in areas adjacent to snow mountains, snowmelts induced by global warming can also augment that increase of water discharge in rivers. As a consequence, adjacent inhabited areas can suffer severe damages.

The river Mangfall in south Bavaria, Germany has a mean discharge of 26.9 m³/s [1]. In the event of 100-year flood, heavy rain and/or snowmelts from the nearby Alps Mountain can raise that figure to 480 m³/s as estimated in [1]. The existing dikes can sustain only the event of a 30-year flood. Such events can put the lives of 40,000 people in danger and cause potential damages of about 1 billion Euros. That makes the flood-prone area of the river Mangfall the riskiest area in Germany. The state of Bavaria put

a plan to construct a retention basin of a total capacity of 6.4 million m³ in order to avoid such consequences. Location of the retention basin is shown in Fig. 1.

In the scope of the works depicted in Fig. 2, Bauer was contracted to install a cut-off wall for the retention dam for the main retention basin as well as other special foundation works like secant pile wall, sheet piles and jet grouting.



Fig. 1: Location of the Detention basin in the vicinity of the Alps Mountain [3]

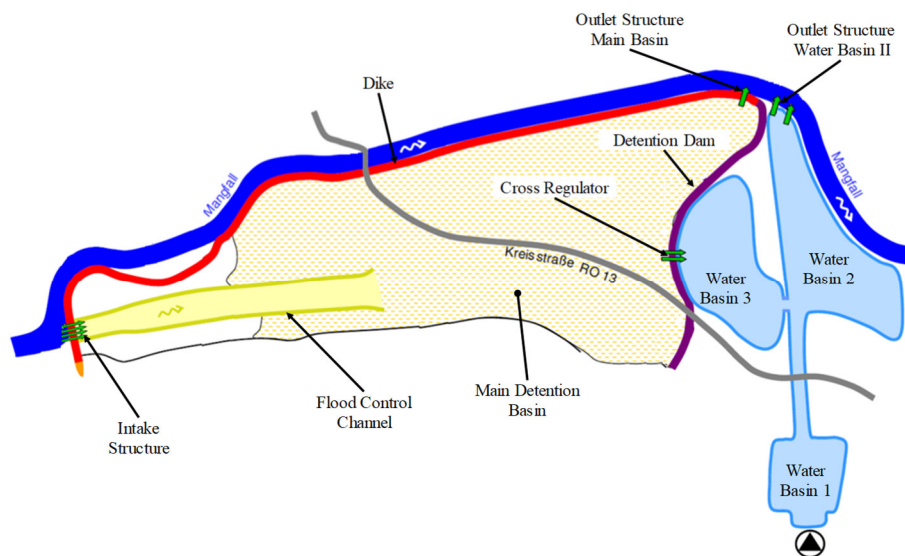


Fig. 2: Scope of works for the detention basin for Mangfall river [23]

The original solution for a major part of cut-off wall was a single-phase cut-off wall using grab with a thickness of 80 cm, while the remaining part was a deep soil mixing wall with a thickness of 50 cm. Bauer proposed to replace the grab single-phase cut-off wall with its Mixed-In-Place technique, MIP. Although the thickness of the proposed

MIP wall was smaller than the required thickness of the single-phase wall, Bauer was able to prove that the MIP wall can fulfill the required system permeability or hydraulic permittivity as the single-phase cut-off wall. One more advantage the alternative solution possesses is that soil waste transport would be much less. In contrast to the grab single-phase cut-off wall, where the self-hardened suspension fluid has to fully replace the excavated soil, in deep soil mixing the existing soil is mixed with the introduced cement slurry and form the cut-off wall when hardened. Through the lower consumption of building material alone, the proposed system enabled the public sector client to save costs for the taxpayers in Germany.

Beside fulfilling the geotechnical task of the cut-off wall there is also the sustainable task which has become more into focus due to the mutual efforts of the United Nations with their claimed 17 Sustainability Development Goals or the European Union with their announced Green Deal to make Europe climate neutral until 2050. In this context it should be mentioned, that although geotechnical works will consume energy and materials and therefore account for greenhouse gas emissions, smart design and application of specific technologies can help to reduce the impact of these works and the construction on the environment. Mixed-In-Place as a construction method, has been proven to allow for a significantly smaller equivalent Carbon Footprint, and for an extremely reduced impact to the neighborhood mainly due to less transports with less traffic required, compared to a classical method based on excavation. To provide clients or other stakeholders with reliable numbers to quantify the specific climate impact of a any geotechnical works, available tools are on the market which might contribute to any such sustainability considerations [4**Error! Reference source not found.**] & [5].

2 Deep Soil Mixing

Deep soil mixing describes the process of introducing a binder to the native soils in order to create a homogeneous mixture of soil and typically a cementitious binder, which has better mechanical properties i.e., strength, stiffness, permeability [7]. Soil mixing techniques were developed for the first time in the U.S in the 1950's as a piling technique. In the 1970's Soil Mixing Walls (SMW) were developed Japan [4]. Over the years many soil mixing techniques were developed and have been used in different application and under various conditions. The Federal Highway Administration of the US transportation department has classified the different deep mixing methods (DMM) in [7] as shown in Fig. 3.

Deep soil mixing has a wide variety of geotechnical applications. Deep soil mixing has been frequently used for soil improvement for different purposes like liquefaction mitigation, improvement of bearing capacity, support of earth embankments, and as foundation elements in some special cases. One more application for deep soil mixing is to construct cut-off walls from the mixed soils, similar to the subject of this paper. Applications also include shoring systems for excavation pits, in case the installed deep

soil mixing elements are fitted with structural elements like steel beams of reinforcement cages.

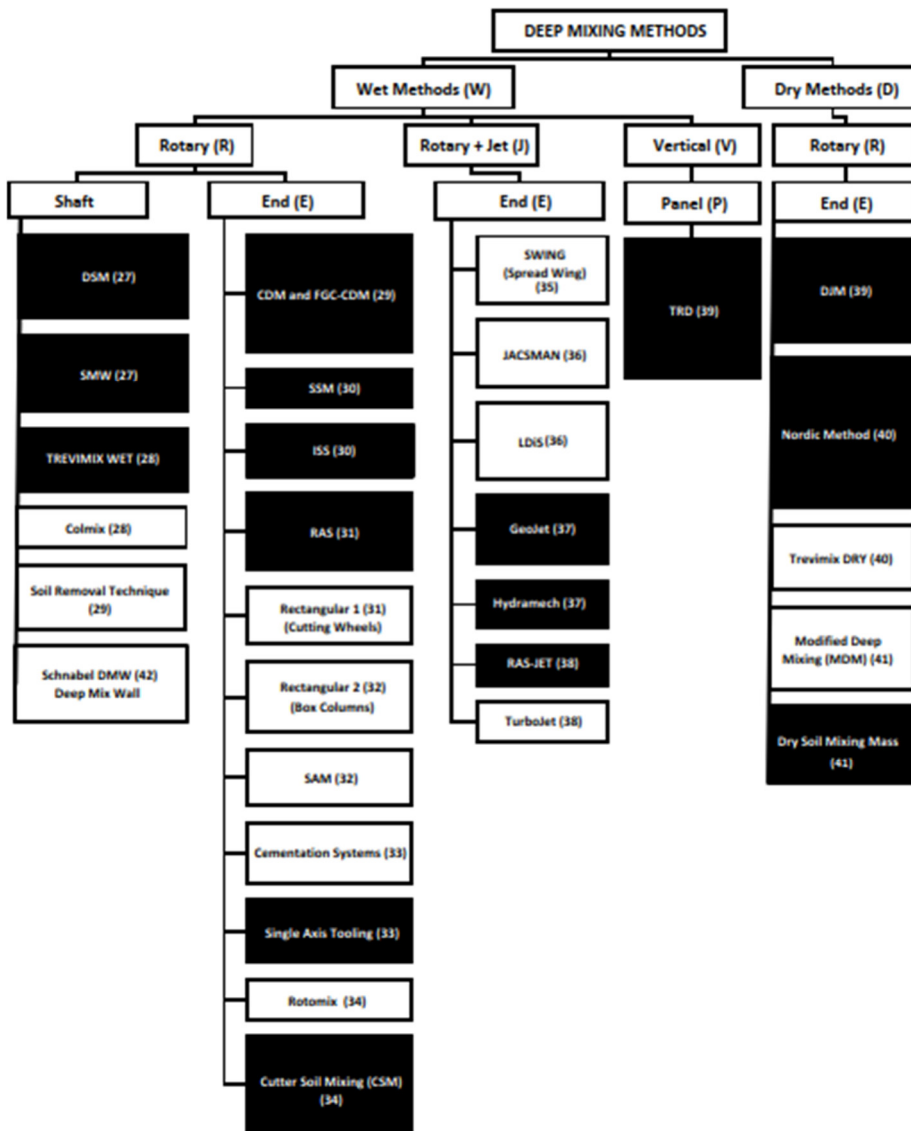


Fig. 3: Classification of Deep Mixing Methods as per FHWA [7]

In general, deep soil mixing techniques demonstrate few advantages in comparison to traditional special foundation techniques. Some of those advantages are having better production rates and hence being a more economical alternative, producing minimal installation impacts of noise & vibrations, causing minimum soil disturbance for

neighbouring buildings, applicability in almost all obstacle-free soil types, and being environmentally friendly because of less produced spoils [8].

On the other hand, deep soil mixing suffers from some drawbacks like its limited depth of treatment, although the reachable depth significantly differs from one method to another. It also cannot deal in the same effective way with very dense or very stiff soils as well as soil layers with boulders. Unlike engineered construction materials like concrete and steel, the characteristics of the produced elements cannot be predicted even for one method at a time. They are rather dependent on the soil conditions at each project.

2.1 Mixed-In-Place (MIP)

In 1987, Bauer developed the Mixed-In-Place Technique, also known as MIP, and applied it in Nuremberg for an excavation support system for the first time. Bauer further developed the technique to what we know today, the triple auger MIP since the early 1990's. Fig. 4 presents a modern rig equipped for MIP as well as a schematic site setup. MIP was successfully applied in different applications and on 3 continents. Applications ranged from landmark projects to small projects. Due to its distinguished mixing quality, MIP were applied in all possible applications for deep soil mixing i.e., cut-off wall, retaining walls for excavation pits, foundation elements, soil mass improvement for liquefaction mitigation, and for increasing bearing capacity of an earth embankment.

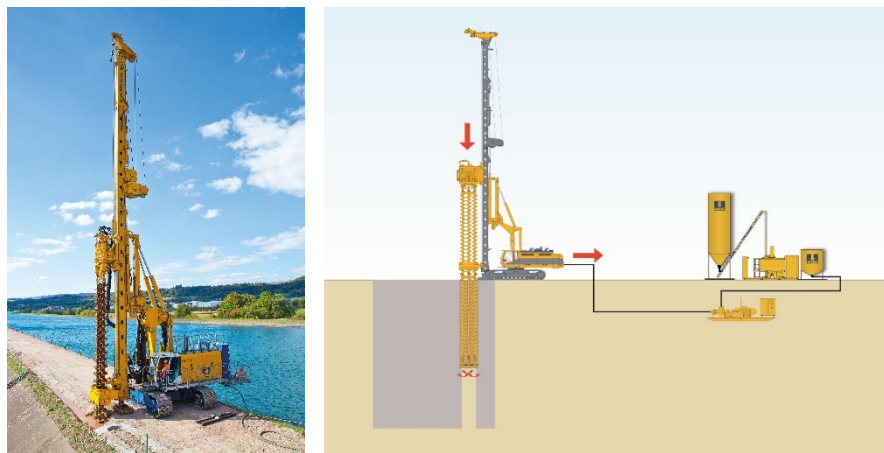


Fig. 4: Modern Rig during installation of a MIP cut-off wall (left), and a typical site setup for MIP works (right)

Currently, MIP walls have nominal thicknesses of 400 mm or 550 mm with depths to nearly 24 m. Adjacent MIP panels form together continuous walls. The panels are constructed using Bauer's patented double pilgrim sequence. Similar to the standard pilgrim sequence for diaphragm walls, primary panels are installed first, before closing the gaps between them with the secondary panels. Additional panels are then installed in the overlap areas between primary and secondary panels, ensuring that each location

within the wall is mixed twice. The triple augers string penetrates the soil while introducing a cementitious slurry till it reach the end depth. Afterwards, the triple augers switch their sense of rotation to start the homogenization process. Additionally, during the upstroke, the triple augers string is moved down and upwards to enhance the homogenization effect.

Through its unique and patented triple auger mixing tool as well as the double pilgrim sequence, MIP can homogenize the cement mixed soil not only locally at each level, but also along the whole panel length. This way it ensures the same mixing quality along the whole panel. In the same way, it can dilute the negative effect of an intermediate unfavourable soil layer along the whole length, which eliminates the presence of weak spots in the same panel.

3 Geotechnical Works

The scope of works in Feldolling – besides the execution of cut-off walls for the sealing of the dam - also included the construction of some buildings that are necessary to operate the retention basin during a flood. Therefore, a bored pile wall (1700 m², D=880 mm), several sheet-pile walls (3300 m²; depth down to 14 m) and jet-grouting (1000 m³) are executed.

For the sealing of the existing soils under the future dam the client planned a grab cut-off wall, D=800 mm, up to ~ 20 m deep. The sealing of the dam itself was planned as soil-mixing wall (e.g., MIP cut-off wall).

3.1 Soil conditions

Before the call for tenders, extensive soil exploration works have been carried out over the full length of the foreseen dam. In figure 5 a part of the underground soil conditions is shown. It depicts the various soil layers within the cut-off-wall with gravel, sand silt and clay.

According to the soil report [9], ancient glaciers in that area formed a basin with tertiary subsoils. On top of the tertiary subsoil, glacier movements brought boulders, gravel and sand. Lakes appeared after the melting of the glaciers and fine-grained soils were washed in and deposited on the ground. Due to heavy movements, growing and reducing size and location of the glacier snout, layers were formed as shown in Fig. 5 as an example. Those varying soil layers was taken into account when planning the execution of cut-off-walls.

3.2 Technical aspects of grab cut-off-wall and MIP-cut-off wall

A specious advantage of the grab single-phase cut-off-wall is that it relies on full excavation of a trench and replacing the soil by a ready-mixed self-hardening slurry which in its relevant properties can previously be tested and adjusted so that it meets the requirements of the project specifications. The fact that –unavoidably– remaining soil and sedimentation of solids within the slurry might alter the characteristics over depth

is practically accepted and actual characteristics are being checked within the well-established QA/QC system. As for Mixed-In-Place technology, the slurry represents only a smaller fraction of the actual cut-off-wall material, and the natural soil is the other fraction. The soil-slurry mixture needs to be suitability tested before execution and later quality tested during the execution of the works.

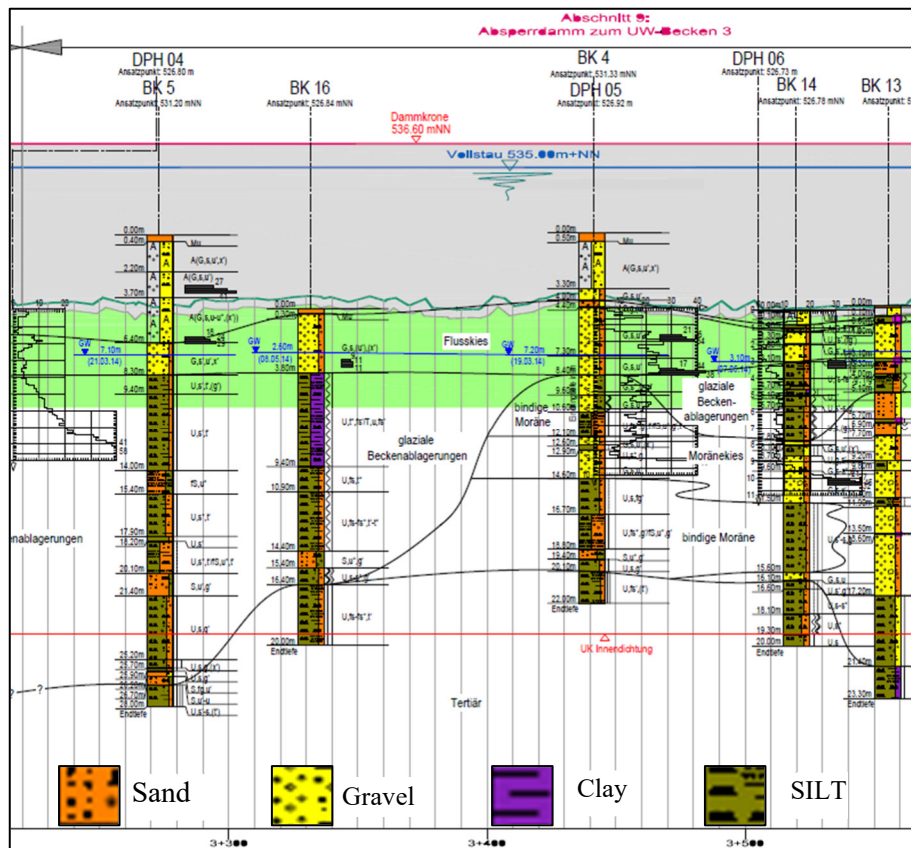


Fig. 5: Typical geotechnical cross section (in German, legend in English) [9]

Also, a grab cut-off wall slurry needs to overcome challenges like trench stability, where it shall support layers consisting only of gravel without sand or fine-grained soils, as it has to completely replace the excavated soils with the self-hardening slurry. On the other hand, this risk is minimized with cement soil mixed wall, as it just added the cement slurry to existing soils, without replacing it. Similarly, the associated efforts to dispose the excavated soils can be completely minimized.

Based on the soil explorations as well as the previous experience of executed MIP-walls the soil was assessed as suitable for the MIP, after additional soil explorations and quality assurance tests were carried out. The replacement of the grab cut-off wall by the MIP-wall required a close coordination with the design engineers of the client. A technical statement was written to prove that the MIP fulfils the exact requirements

of the contract. Chapter 4 describes that matter more intensively. Nevertheless, about 6300 m² partially reinforced grab cut-off wall was constructed because of depths of up to 40m as one section, which could not be reached by MIP (max. 24 m of depth).

4 Quality

In principle, all civil works carried out for the construction of the flood retention basin were subject to certain pre-specified and demanded quality controls. Especially for the deep soil mixing technique, it had to be proved that the MIP was suitable for the existing soil conditions not only based on previous experience but also on the basis of laboratory testing.

4.1 Quality assurance

Firstly, the client and his Engineer had to be approve that MIP is technically equivalent to the grab cut-off wall. For that, Bauer technical department provided a technical note, in which they compared the MIP characteristics to the project specifications that are fulfilled by a grab cut-off wall. In the following the most important requirements of the project specifications are listed:

- Nominal thickness 80 cm
- Depth: 5-30 m; embedment in sealing soil layer
- Overlapping of panels at the top: 25 cm
- Minimum wall width: 50 cm (30 m depth)
- Verticality: Proof by inclinometer measuring
- Compressive strength: $1 \leq f_{m,k} \leq 3$ MPa after 28 days
- Permeability: $k_f < 10E-8$ m/s
- Temperature: $> 5^\circ\text{C}$

In the technical note it was demonstrated, that the MIP-cut-off wall can fulfil all requirements. The nominal wall thickness of the MIP was one of the most important quality issues, as it was only 55 cm instead of the required 80 cm. However, the function of the cut-off wall depends on the impermeability of the cut-off system and not only on the nominal thickness. Therefore, sure had to be made that the MIP-wall can deliver a system-permeability as required in the specifications. Tests in the laboratory were carried out and the required system-permeability was demonstrated. The tests were done using soil samples collected during an additional testing campaign. The campaign had two objectives: First, to make sure that the MIP-wall can embed into the sealing soil layer. Secondly, to obtain adequate soil samples for the laboratory tests.

Stiffness of the MIP material. The laboratory tests had to be done carefully, because it was necessary to estimate the influence of the different amounts of cohesive and non-cohesive soils. Producing the MIP in areas with mainly gravel and sand will lead to higher wall strengths. But as the list above shows, strengths over 3 MPa were not allowed, as too big compressive strengths are correlated to higher stiffnesses. When the future dam is constructed, settlements and deformation of the dam will occur during the first flooding of the retention basin. Therefore, the stiffness of the cut-off wall must be limited to accommodate such deformation without developing any cracks. On the other

side, the minimum required compressive strengths of 0.5 MPa has to be attained to avoid any erosion of the MIP-wall during floods. The obtained original soil was mixed with different mix recipes to ensure that in all cases, with the existing soil stratification and particle size distribution, the boundaries of the compressive strength can be maintained.

Depth of the MIP-wall. The requirement to drill down to depths of 30 m turned out to be not necessary demonstrated by the additional soil exploration campaign. A maximum depth of 22.5 m was sufficient for the cut-off, which was possible for the MIP equipment to reach. As described in 2.1, using MIP continuous walls can be installed. The minimum wall width was defined as 40 cm, otherwise there could be the system permeability will not be given. The wall width at the top of each MIP-panel is still 55cm, but because of drilling deviations the overlapping at the bottom of the MIP-panels can be smaller. Therefore, inclinometers were installed in 2 of 3 augers to measure the verticality of each panel, which is depicted on the screen of the rig operator in real time. That enables the operator to react to bigger drilling deviations because of unexpected obstacles in the underground. Hence, the rig operator can easily install another panel in the area with bigger deviations, while the slurry is still fresh and maintain the minimum thickness of the MIP wall at the bottom. The combination of using inclinometer to measure the verticality and GPS to get the exact location of each panel at the top makes it possible to depict the as-built for the MIP wall in CAD software and thus prove that the wall has no severe deviations and installed as per the project specifications.

Permeability of the MIP material. The permeability to be reached has to be half of the originally required specification for the grab single-phase cut-off wall, as the cut-off wall thickness was reduced to 40 cm (instead of the originally specified 80 cm). Thus, the system permeability was assured. That was proven through laboratory tests prior to construction. As the MIP execution works took place in the spring and summer of 2021, the required temperature of $> 5^{\circ}\text{C}$ was always achieved.

Additional QA measures. Additional risk mitigation measures were also prescribed in the technical note of the MIP in order to have agreed solutions for any foreseen problems that might occur. To avoid any misinterpretation of some single compressive strengths results (being too big or too low), it was mandatory to collect more samples than needed of the same area. It was also possible with the help of the narrow soil exploration raster to optimize the mix recipe of the slurry for the different soil profiles, even for predominant cohesive and non-cohesive soil profiles.

Before the commencement of the MIP a detailed QA-plan was crafted according to the technical note, project specifications and in agreement with the client's Engineer. The QA-plan described the scope of all quality control works required to ensure that the constructed MIP wall is fulfilling the project requirements. It included which kind of tests, the required frequency, where and how to conduct the tests as well as the acceptable limits.

4.2 Quality control

During the works of the MIP-wall all quality tests and checks were carried out according to the QA-plan. This section presents some of the carried-out quality control tests.

Machine protocols. First, in order to monitor the amount grout slurry mixed with the soil, machine protocols were generated for each MIP-panel, which recorded the grout volume injected into the soil vs. the depth, as shown in Fig. 6.

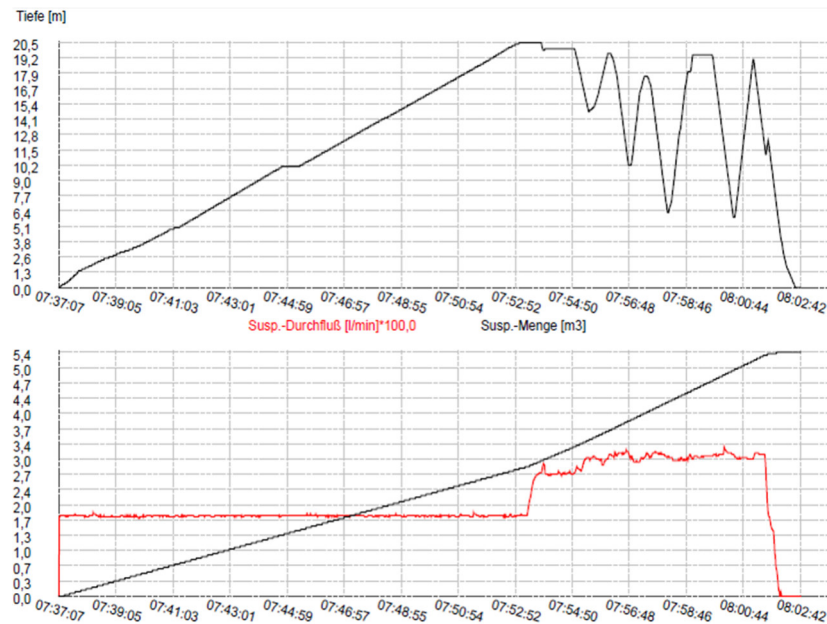


Fig. 6: Machine protocol of a MIP-panel (depth & flow rate over time)

That makes sure and comprehensible that the right amount of cement has been mixed with the soil, which ensures that required stiffness of the MIP can be achieved. The production documentation also includes information about the name of the panel, date, depth, operator's name, and time consumed for that panel.

Properties of fresh slurry. In addition to the machine protocols, the slurry was tested before it is mixed into the ground. Under normal conditions the mixing plant works with calibrated scales that mix predefined amounts of cement, bentonite and water together. Several slurry tests were executed each day. The test results must be within the predefined range, that was set in advance by the technical department and agreed with the client's Engineer. The following tests were executed and documented:

- Density (test with suspension scales)
- Temperature
- pH-value
- Marsh-time
- Sedimentation behavior

The above-mentioned tests made sure that the slurry was mixed correctly and corresponded closely to the one used in the suitability test done prior to the execution time. Controlling the density showed that the correct amounts of cement, bentonite and water were mixed together. The mixing temperature was also controlled and had not to exceed 35°C or fall below 5°C as it can hinder the hardening process. The pH-value is a typical QC test for self-hardening slurries and adopted for MIP, mainly to allow for another test to verify a consistency in mixing the cement-bentonite slurry, and significant changes would cause raising a red flag to double-check the mix proportions at the batching plant. The marsh-time test measured the viscosity of the slurry to ensure that the working characteristics (pumping ability and stability in different soils) of the slurry was ensured. The sedimentation behavior tests are also carried out to further ensure the stability of the slurry as well in the slurry vessels as in the panel.

Properties of hardened cement soil mix. The third part of the quality control checks included the compressive strength and permeability tests, which were executed in the predefined frequency in the QA-plan. The testing times were 7 and 28 days after collecting the samples (both from fresh slurry and from different depths of the mixed panel). Tests after 7 days gave an early indication whether the development of compressive strength was adequate and facilitated quick measures, in case the strength development was not promising like by installing additional panels around the executed panels with insufficient strength development. The 28 days tests showed compressive strengths within the predefined and originally specified range (1-3 MPa), as shown in

Fig. 7.

Proben-Nr.	Baust.-Nr.	Prüfdatum	Höhe mm	Durchmesser mm	Gewicht kg	F_m kN	Alter [d]	Rohdichte kg/m ³	f_{mi} N/mm ²
38723	27	04.05.2021	96,0	99,0	1,445	13,92	28	1955	1,81

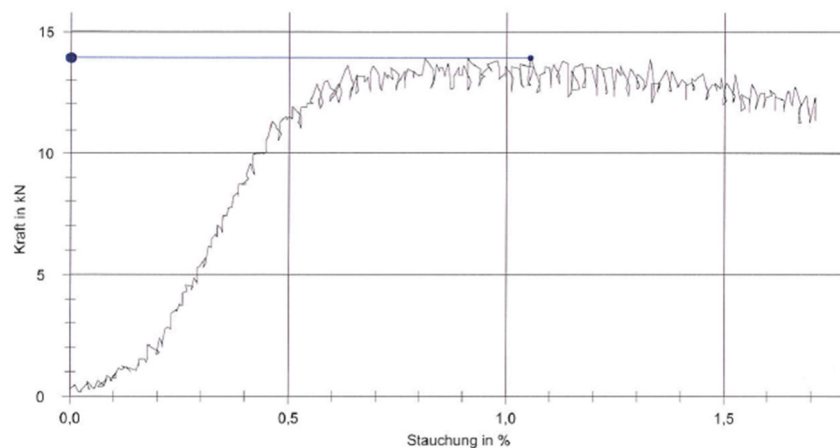


Fig. 7: Extract from lab results report showing the compressive strength of MIP sample

5 Conclusion

Cut-off walls are an integral part of dams, dikes, and levees where they act as a water sealing barrier. Traditional techniques to install cut-off walls like diaphragm walls (grab or cutter) can be successfully replaced by soil mixing techniques. MIP technique is one of these soil mixing techniques, which can produce cement soil mixed walls, that can fulfill equivalent requirements for cut-off wall using the traditional techniques. This paper presents a project where Bauer Spezialtiefbau GmbH installed a MIP wall as cut-off wall in the scope of the construction of the flood retention basin in Feldolling, Bavaria, Germany. Despite the non-uniform soil conditions, which is a major component of the end product, along the cut-off wall axis, the MIP technique could deliver a homogeneous wall. That could be achieved by the implementation of a sound QA-plan, based on Bauer's experience from previous projects.

Soil mixing walls are a more cost-effective option as they use the existing soil as aggregates. As substantial amounts of construction material are saved in this way, they are also considered to be more sustainable. Also, as less construction material is used, less site transports are required, which again contributes in reduction of the cost and the carbon footprint of the project.

References

1. Deutsches Gewässerkundliches Jahrbuch, Donaugebiet 2006: Bayerisches Landesamt für Umwelt (Bavarian State Office for Environment).
2. Hochwasserrückhaltebecken Feldolling Zweck, Betrieb Bemessung und Fundtionsweise 2013: Wasserwirtschaftsamt Rosenheim (Water Management Authority in Rosenheim)
3. Google Maps, <https://www.google.com/maps/place/Leitzachwerk+Staubecken/@48.3054234,11.4682282,7.83z/data=!4m5!3m4!1s0x479df6c9b2a4d4ab:0x86880a59004468c8!8m2!3d47.8846676!4d11.8753044!5m1!1e4?hl=en>, last accessed 2022/07/25
4. Ibuk, H., et al.: Dry excavation pits installed with smaller carbon footprint by soil mixing, Deep Mixing Conference, DFI, Gdansk, Poland, 2020/2021
5. Bauer, F., et al: Sustainable Products for Geotechnical Works. EFFC / DFI International Conference on Deep Foundations and Ground Improvement. Smart Construction for the Future. Berlin. 2022
6. An Introduction to the Deep soil mixing methods as used in geotechnical applications- Ch.2: US Department of Transportation, Federal Highway Administration (March 2000)
7. An Introduction to the Deep soil mixing methods as used in geotechnical applications-Ch.1 & Ch.11: US Department of Transportation, Federal Highway Administration (October 2013)
8. Topolnicki, M.: General overview and advances in Deep Soil Mixing. In: XXIV Geotechnical Conference of Torino Design, Construction and Controls of Soil Improvement Systems, Torino (2016)
9. Baugrundgutachten, Hochwasserrückhaltebecken Feldolling, 2015
10. Laboratory results for compressive strength testing for project Feldolling, May 2021